

Pipeline Integrity Assessment Using Probabilistic Transformation Method and Corrosion Growth Modeling Through Gamma Distribution

K. Younsi, A. Chebouba, and N. Zemmour, Université de Boumerdes, Algeria, and A. Smati, Université de Boumerdes and Pegaz Engineering

Summary

This paper presents a methodology to estimate the probability of failure of every individual corrosion defect and the residual likelihood of failure of an overall corroded pipeline segment after selected repairs, using structural probabilistic analysis based on the assumption of a stationary gamma distribution of the corrosion process. Metal loss size is taken as the load condition, and the allowable depth of the defect is taken as the resistance condition. The load condition is obtained applying the probabilistic transformation method (PTM) and the resistance condition is obtained through Monte Carlo simulation.

Using inspection data collected on a gas pipeline segment pigged two times, results of the suggested methodology are compared with those obtained by a classical approach based on a Gaussian distribution. It is determined that the use of Gaussian model overestimates for a short time horizon after inspection the failure probability, and suggests many useless repairs. The model developed in this paper instead authorizes a more rigorous estimation of failure probability and a significant reduction of maintenance costs.

Introduction

Probability of failure increases while pipelines become aged, and maintenance and rehabilitation strategies should be based on the prediction of the pipeline resistance behavior with time. Corrosion can be defined as a dynamic and complex destructive attack on pipelines. It is related to the physical properties of the pipeline, its surrounding environment, its mechanical properties, its coating, and the efficiency of its cathodic protection (Ahmed and Melchers 1996, 1997). The deterioration mechanism caused by corrosion is made possible once the pipeline is pigged several times. Nevertheless, because of the considerable length of pipelines carrying hydrocarbons, inspection by smart pigs is expensive, and its planning must take limited resources into consideration. Though the interval between two inspections is important, the longer that interval, the greater the uncertainty about the deterioration state of the pipeline. In this context, mathematical models are to be developed in order to serve as a way to optimize maintenance planning and to allow a quantitative evaluation of the remaining probability of failure during the interval between two inspections.

To estimate the failure probability of a corroded pipeline, corrosion rate is the fundamental parameter to be assessed. This evaluation is based on the comparison of the sizes of defects in successive ILI inspection runs (Worthingham et al. 2002). To make prediction of this deterioration possible, a minimum of two sequential inspections is theoretically required.

Structural Probabilistic Analysis and Quantitative Estimation of Failure Probability

Because of the influence of corrosion variability, resistance uncertainties, tool accuracy, and geometrical dimensions of the pipeline, many authors recommend the use of probabilistic analysis (Desjardins 2003; Alamilla et al. 2009). Deterioration-process evolution over time is uncertain, and it can be represented using a stochastic procedure. In this context, structural reliability approaches were applied from several years in many fields, in particular from nuclear and civil engineering.

Probabilistic structural analysis can be defined as the formulation of a mathematical model to calculate the probability of a structure to be in a specified state, taking into account randomness of its load and/or resistance properties, or the unknown values of same. The limit state is defined where the load and resistance conditions are equal. Once the load condition is greater than the resistance condition, failure occurs.

Considering that the load condition S and resistance condition R are, respectively, defined by the density of probability functions $f_s(s)$ and $f_R(r)$, the probability of failure P_f is then given by

$$P_f = P(g = R - S \leq 0) = \iint f_{RS}(r, s) dr ds, \dots\dots\dots(1)$$

where g is the performance function and $f_{RS}(r; s)$ is the probability of density function.

Almost all of the quantitative approaches adopted use the load-resistance models under several assumptions of statistical distributions of operating pressure, maximum operating pressure, and corrosion rate. In the case of a corroded pipeline, it is judicious

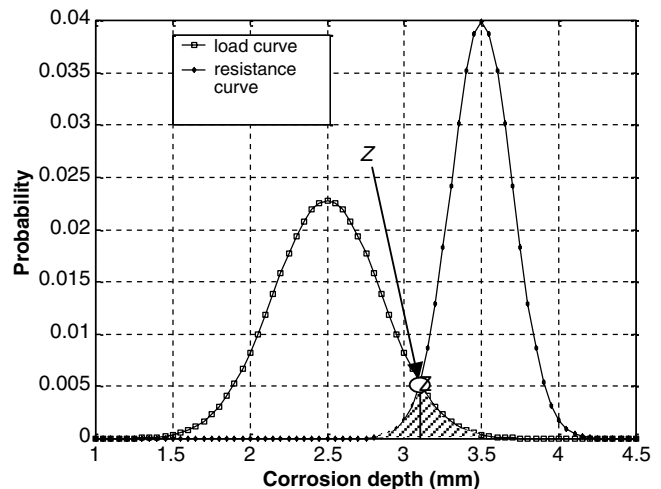


Fig. 1—Failure area.

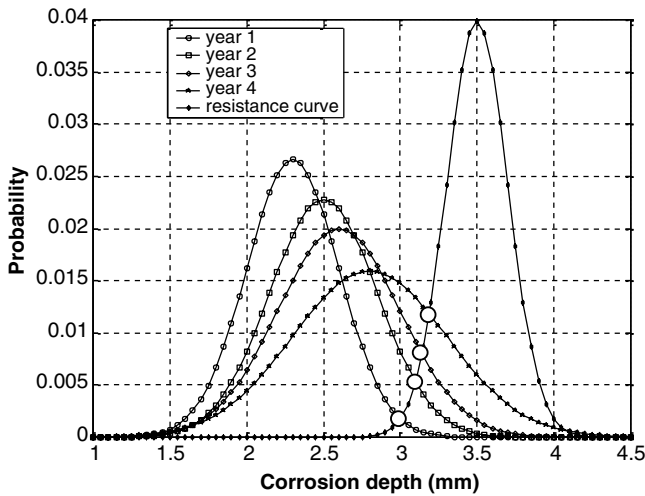


Fig. 2—Resistance curve and load-function evolution with time.

to consider metal loss as the load condition and the allowable dimensions of the defect as the resistance (Younsi and Smati 2005). Otherwise, failure occurs once corrosion depth x reaches the critical depth x_{cr} . Failure probability is then equal to the surface represented by the hatched area in Fig. 1, where Z represents the intersection point between load and resistance functions.

The main advantage of such representation lies in its simplification of the problem, which becomes a function of corrosion depth only. However, because of the dynamic nature of the deterioration process, the load is a time-related function and is increasing. By contrast, the resistance condition remains constant (Fig. 2).

Splitting the interval of time, separating two inspections, into N elementary intervals Δt and putting $t_i = i\Delta t$, the probability of failure at t_i can be given as

$$P_f(\tau_i) = P(g(\tau_i) = X_{cr} - X(\tau_i) \leq 0) \dots\dots\dots(2)$$

$$= \int_{Z(\tau_i)}^{+\infty} f_X(x, \tau_i) dx + \int_{-\infty}^{Z(\tau_i)} f_{X_{cr}}(x) dx.$$

Resistance Curve Modeling

As a deterministic model, recommendations found in the works of Kiefner et al. (1973) and Kiefner and Vieth (1990) are frequently used. These works have the ASME B31G as a root (1991) (Appendix A)

Assuming that uncertainties in mechanical properties and geometrical parameters in Eq. A-3 are described using normal and log-normal distributions with a known mean and variance (Lee and Pyun 2002), the resistance distribution can be expressed through the Gaussian probability density function:

$$f_{X_{cr}}(x) = N(x / \mu_{X_{cr}}, \sigma_{X_{cr}}) \dots\dots\dots(3)$$

$$= \frac{1}{\sigma_{X_{cr}} \sqrt{2\pi}} \exp\left[-\frac{(x - \mu_{X_{cr}})^2}{2\sigma_{X_{cr}}^2}\right],$$

where $\mu_{X_{cr}}$ mean of critical defect depth and $\sigma_{X_{cr}}$ standard deviation of the critical defect depth are estimated by Monte Carlo simulation and defined once for each section of a given thickness and pressure.

Load-Curve Modeling and Probability of Failure Calculation

The majority of probabilistic structurally oriented analyses works performed assume a Gaussian distribution, linear or nonlinear, to describe the deterioration process. In recent years, some pub-

lications suggest a gamma distribution to describe the deterioration process (van Noortwijk et al. 2007). However, these works are mainly directed toward the determination of the optimal periodicity of the inspections, but do not allow definition of the probability of failure associated with a given state of degradation.

Whatever the main assumption, the principal parameter to define the load curve and evaluate the probability of failure with time depends on the accuracy in determining corrosion rate. Corrosion-rate estimation, however, is related to measuring the metal-loss depth evolution:

$$V_i = \frac{x_{i2} - x_{i1}}{t_2 - t_1}, \dots\dots\dots(4)$$

where x_{i2} is the maximum depth of a feature i in Run 2 on date t_2 and x_{i1} is the maximum depth of a feature i in Run 1 on date t_1 .

In a corroded pipeline, every segment may contain hundreds to thousands of corrosion defects with different sizes. Subsequent to the matching process of corresponding defects, mean and standard deviations of corrosion rate can be calculated as follows:

$$\mu_v = \frac{1}{N} \sum_{i=1}^N V_i, \dots\dots\dots(5)$$

$$\sigma_v = \sqrt{\frac{1}{N} \sum_{i=1}^N (V_i - \mu_v)^2}. \dots\dots\dots(6)$$

Gaussian Distribution of Corrosion Growth Rate

Assuming a linear representation of corrosion process given by

$$x(\tau) = x_0 + V\tau, \dots\dots\dots(7)$$

and a Gaussian distribution of corrosion growth

$$f(V) = N(V / \mu_v, \sigma_v)$$

$$= \frac{1}{\sigma_v \sqrt{2\pi}} \exp\left[-\frac{(V - \mu_v)^2}{2\sigma_v^2}\right], \dots\dots\dots(8)$$

probabilistic load-curve evolution with time is given by the following:

$$f_{X(\tau)}(x) = N(x / \mu_X(\tau), \sigma_X(\tau)) \dots\dots\dots(9)$$

$$= \frac{1}{\sigma_X(\tau) \sqrt{2\pi}} \exp\left[-\frac{(x - \mu_X(\tau))^2}{2\sigma_X^2(\tau)}\right]$$

with

$$\mu_X(\tau) = x_0 + \mu_v \tau, \dots\dots\dots(10)$$

$$\sigma_X^2(\tau) = \sigma_v^2 \tau^2, \dots\dots\dots(11)$$

where x_0 represents corrosion depth reported in the last inspection.

The area of failure surface between the resistance curve and the intersection point is reached by integrating the resistance curve

$$\int_{-\infty}^Z f_{X_{cr}}(x) dx = F_{X_{cr}}(x) \dots\dots\dots(12)$$

$$= \Phi\left\{\frac{Z - \mu_{X_{cr}}}{\sigma_{X_{cr}}}\right\}$$

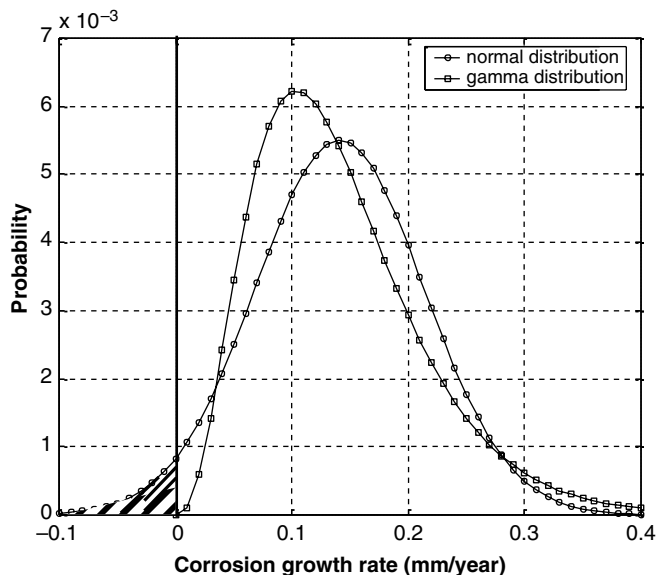


Fig. 3—Growth-rate corrosion modeling using normal and gamma distributions.

However, the failure surface included between the intersection point and the load curve is reached integrating the following load curve:

$$\int_Z^{+\infty} f_{X(\tau)}(x) dx = \bar{F}_{X(\tau)}(x) \dots \dots \dots (13)$$

$$= 1 - \Phi \left\{ \frac{Z - \mu_X(\tau)}{\sigma_X(\tau)} \right\}$$

Φ is the cumulative function of the normal distribution.

The probability of failure is then determined summing the two areas:

$$P_f = \bar{F}_{X(\tau)}(x) + F_{X_{cr}}(x) \dots \dots \dots (14)$$

Gamma Distribution of Corrosion Rate

Treatment of data gathered from a pipeline pigged several times indicates that normal distribution of parameters is no longer justified (Fig. 3). The choice of this distribution is supported by its mathematical ease. The corrosion process is an irreversible process and cannot agree with negative values of the corrosion growth rate. Modeling the corrosion rate with a normal distribution proved in certain works that it is truncated with negative values (Desjardins 2003). This truncation, even if it seems to be logical in the sense that negative values do not have a physical meaning, leads to some information loss which can have a negative impact on the estimation efficiency. This disadvantage can be avoided using

TABLE 1—GAS PIPELINE CHARACTERISTICS

Pipeline Characteristics	
Length	80 km
Diameter	40 in.
Wall thickness	12,7 mm
Steel type	X60
Minimal stress	410 N/mm ²

strictly positive distributions of the gamma family (Younsi and Smati 2005; van Noortwijk et al. 2007). More gamma distribution is versatile and able to take different form of distribution, including normal distribution.

Gamma distribution is given by the following expression:

$$f(V) = Ga(V / \alpha, \beta)$$

$$= \frac{\beta^\alpha}{\Gamma(\alpha)} V^{\alpha-1} \exp(-\beta V); V > 0, \dots \dots \dots (15)$$

with

$$\alpha = \left(\frac{\mu_V}{\sigma_V} \right)^2 \dots \dots \dots (16)$$

$$\beta = \frac{\mu_V}{\sigma_V^2}, \dots \dots \dots (17)$$

where α =scale parameter and β =form parameter.

On the other hand, the transformations in Eqs. 10 and 11 are valid only for the normal distribution family. For this reason, passing from corrosion-rate distribution toward the load-curve distribution with time becomes an issue.

In this work, to avoid this drawback, transition from corrosion-rate distribution to load-curve distribution with time, assuming a linear corrosion process described in Eq. 7, is made possible using the PTM (Soong 1973; Kadry et al. 2007), and the load curve can then be expressed as follows (Appendix B) :

$$f_{X(\tau)}(x) = \frac{1}{\tau} \frac{\beta^\alpha}{\Gamma(\alpha)} \left(\frac{x - x_0}{\tau} \right)^{\alpha-1} \exp \left(-\beta \left(\frac{x - x_0}{\tau} \right) \right) \dots \dots \dots (18)$$

To evaluate the probability of failure, this method is similar to the approach described in the previous paragraph. However, the part of the failure surface between the intersection point and the load curve is obtained using a numerical integration. Intersection points $Z(\tau)$ between the load and resistance curves can be defined resolving the following optimization model:

$$\left[f_{X(\tau)}(x) - f_{X_{cr}}(x) \right]^2 \Rightarrow \text{Min}, \dots \dots \dots (19)$$

TABLE 2—SUMMARY OF INSPECTION RESULTS

	Inspection 1	Inspection 2	Number of Matched Defects
Inspection tool	MFL	MFL	—
Number of corrosion points found	4294	5307	940
Maximum depth of corrosion defect found mm	9,90	10,30	—
Corrosion quality	External	External	—

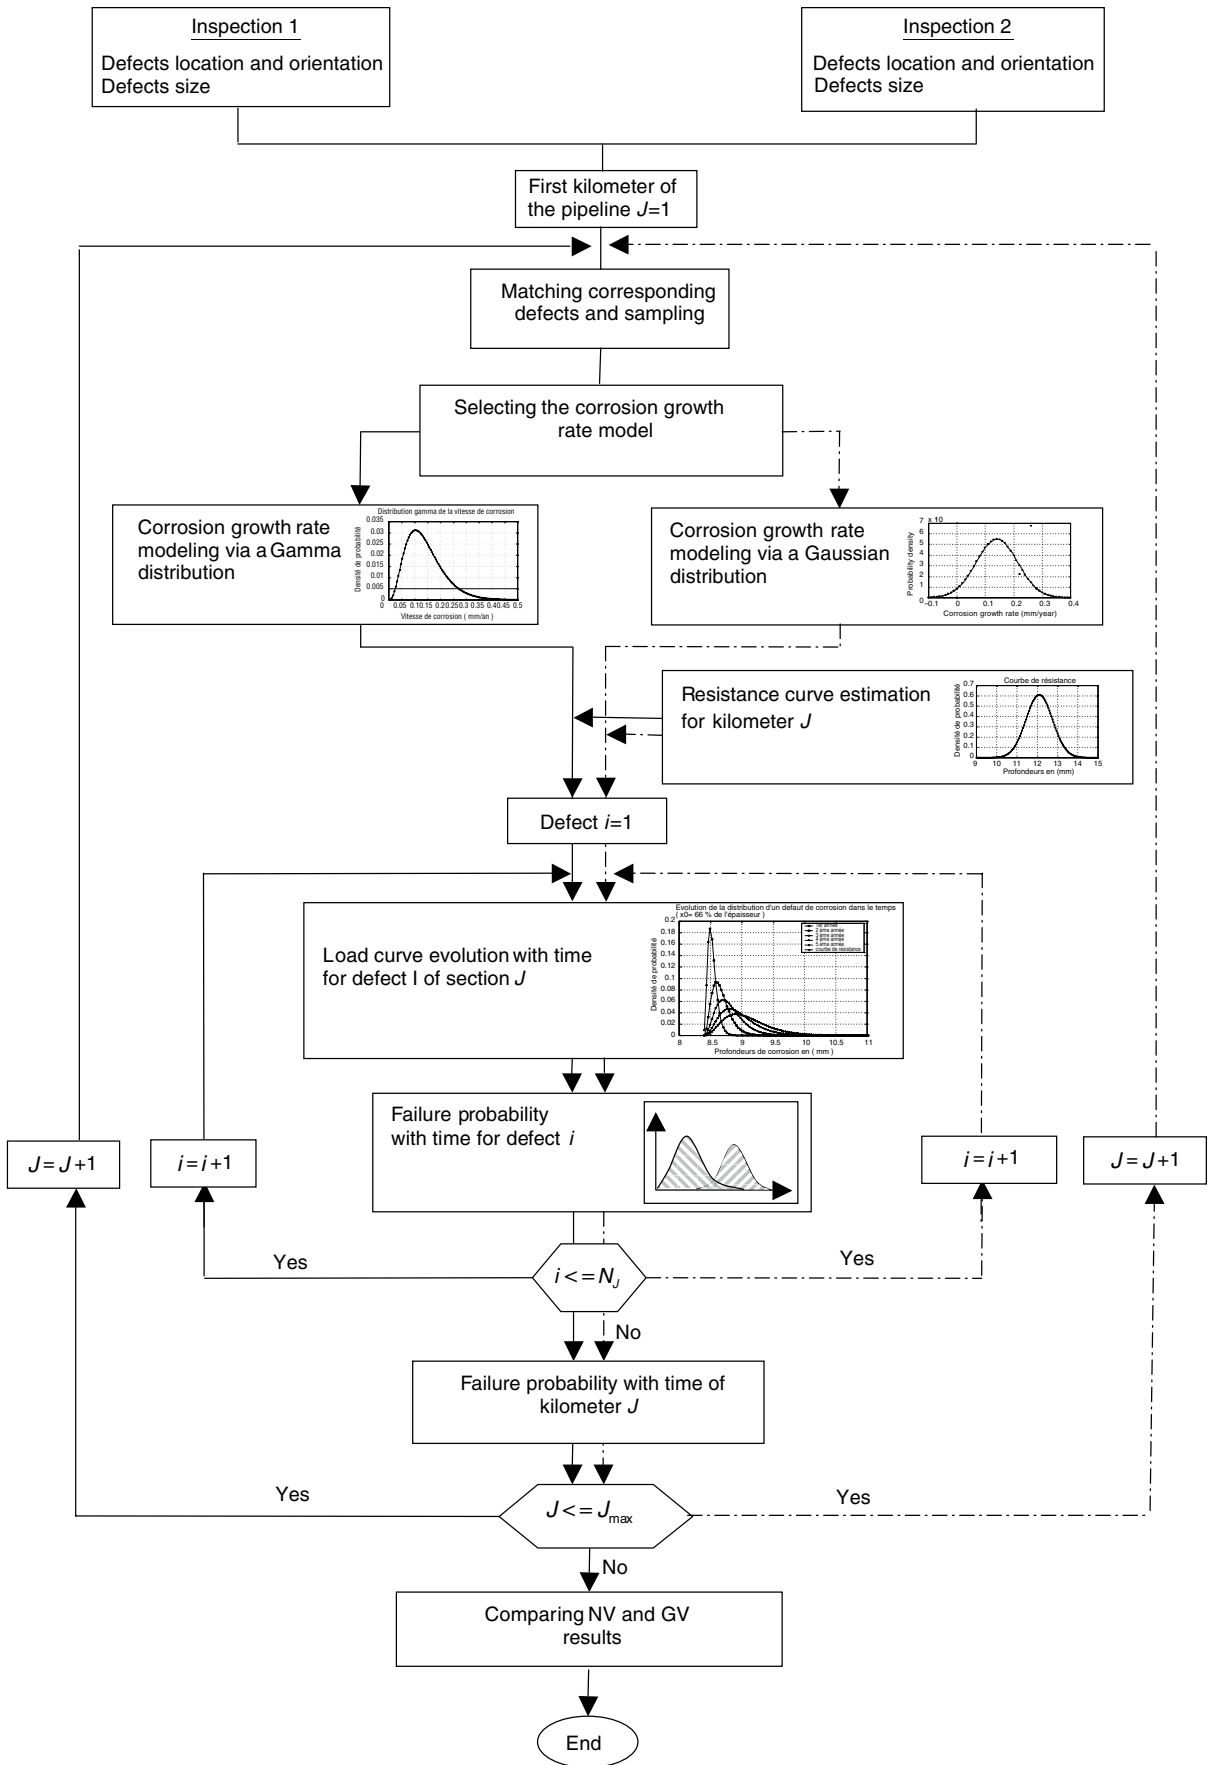


Fig. 4—Computation diagram.

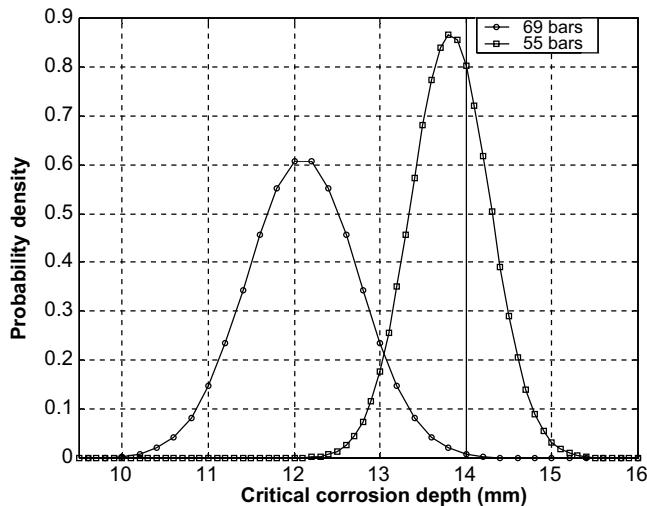


Fig. 5—Resistance curves distribution.

with

$$\mu_x(\tau) < x < \mu_{x_c} \dots\dots\dots(20)$$

Probability of Failure Before and After Repairs

An optimal planning of preventive repairs can be established by simulating failure probability before and after repair of every corrosion defect and comparing results to a threshold criterion adopted by the operator. “Threshold value” used in worldwide practice refers to the failure probability by kilometer (DNV RP-F101 2004). In a corroded pipeline, every kilometer may contain many corrosion defects with different sizes. Following reliability theory and assuming that corrosion defects are independent elements installed in a series (Lee and Pyun 2002; Lecchi 2011), the probability of failure at τ of the pipeline section J can be given as follows:

$$P_{fJ}(\tau) = 1 - \prod_{i=1}^{N_J} (1 - P_{fJi}(\tau)), \dots\dots\dots(21)$$

where P_{fJi} = probability of failure of a corrosion defect i of the kilometre J and N_J = number of corroded defects within the kilometre J .

It can be concluded from this assumption that the probability of failure of a segment must be determined from probabilities of failure of every corrosion defect detected. Every defect contributes to the calculation of the whole failure probability.

Consequently, a pipeline section containing a high number of defects of average size can be, in certain cases, more dangerous than a section with a smaller number of defects with significant corrosion dimensions. This fact is more often ignored in practice where the analysis is performed using the known standards and is performed defect per defect.

Inspections are followed by a preventive intervention program. This program can be established using the estimated probability of failure. This value is determined by applying the relation in Eq. 21 and allocating a probability of zero for every corrosion defect planned for repair. This reduces N_J by a quantity equivalent to a number of repaired defects. Combination of the model in Eq. 18 and the relation in Eq. 21 allows the elaboration of an experimentation stand where the influence of actions, like repairs and segment replacement, on the probability of failure estimation can be simulated beforehand. In the same way, an optimal planning of the future inspection date can be performed.

Case Study: Algerian Natural Gas pipeline

The following application concerns a segment of 80 km of an Algerian natural gas pipeline, with the illustrated characteristics in

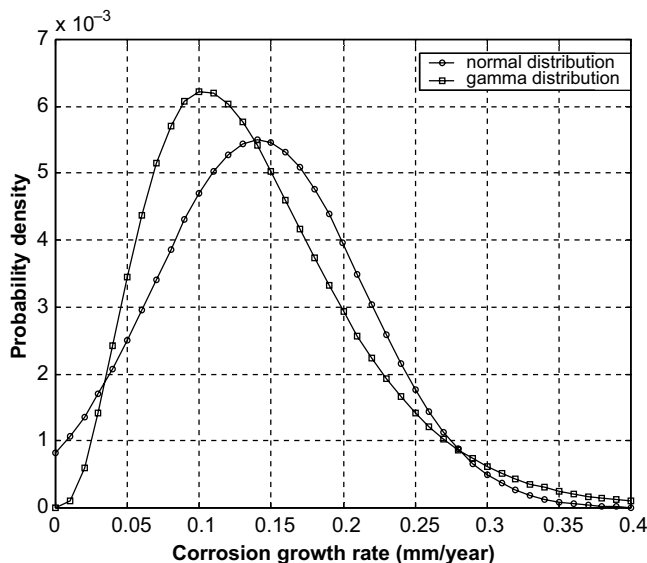


Fig. 6—Corrosion growth rate using normal and gamma distributions.

Table 1. The facility was pigged two times with 5-year intervals (Table 2).

To take into account the spatial variability, the whole pipeline is divided into sections, and defects are grouped into classes according to their depths. Probability of failure estimation for each value τ_i is then obtained following several steps (Fig. 4).

Fig. 5 represents the resistance curves associated to two different operating pressures (corresponding to two different locations of the gas pipeline) obtained using Eq. 3 and the model described in Appendix A.

Results of corrosion growth-rate modeling using normal and gamma distributions are represented in Fig. 6, and subsequent load curves are estimated using the relations in Eq. 9 that we assign as “NV model” and Eq. 18 that we assign as “GV model,” respectively, in Figs. 7 and 8.

Fig. 9 represents, for two different initial corrosion depths, the probability density function after 5 years, estimated using the NV and GV models. The degree of agreement with the histogram obtained from the real data after two inspections is quantified by χ^2 criteria. These results show the best-quality estimation of the GV model.

Fig. 10 represents the failure probability evolution with time on the basis of the NV and GV models. Two values of operating pressure and different initial depths are taken into account.

The following can be concluded from these results that:

- For small initial corrosion depths, characterized by a low probability of failure, the NV model overestimates the failure probability for a short time horizon after inspection (1 to 2 years) and underestimates it for long intervals (4 to 5 years). In addition, the more the operating pressure increases, the more the intersection points between NV and GV curves tend to move to the right side.
- For significant initial corrosion depths, characterized by high probabilities of failure, the NV model overestimates the failure probability for a short time horizon after inspection and gives similar results as the GV model for long periods.

In practice, post-inspection repairs are carried out just after the inspection and concern defects with significant depth of the metal loss. Thus, from the previous conclusions, the use of NV models leads to many unnecessary repairs and increases significantly maintenance costs.

For the whole gas pipeline, treatment of inspection data is performed using three approaches (Table 3):

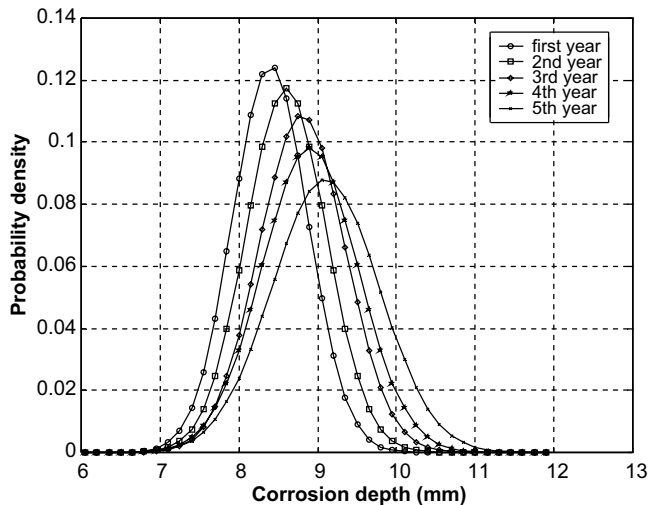


Fig. 7—NV load-curve evolution with time ($X_0 = 66\%$ of the wall thickness).

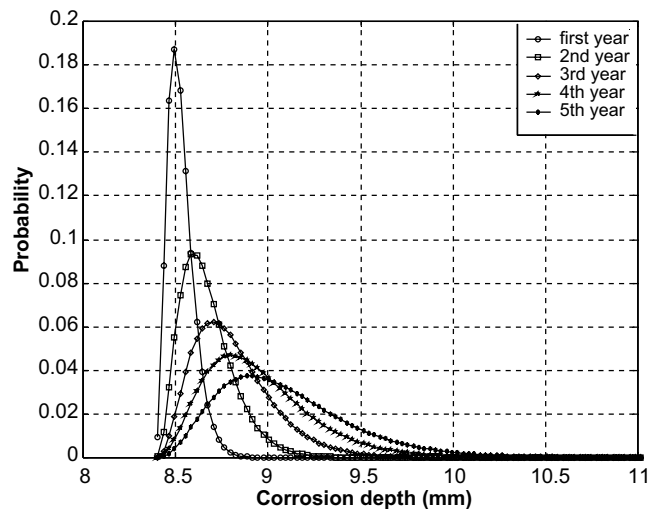


Fig. 8—GV load-curve evolution with time ($X_0 = 66\%$ of the wall thickness).

- The ASME B31G approach (1991) (Appendix A)
 - The reliability structural approach, based on the NV model.
 - The approach developed in this paper, based on the GV model.
- The results are summarised in Table 3.

Figs 11 and 12 represent, respectively, the probability of failure evolution with time of a segment estimated with the NV and GV models. Repairs were assumed to be performed every year on the segment with a probability of failure over 10^{-3} before repairs.

Conclusions

Pipeline inspection results using smart pigs provide a static picture characterizing the deterioration state of the pipeline at the moment of inspection. Because of the dynamic and the random nature of pipeline corrosion, these results can be represented by a stochastic process related to time. In this context, using Gaussian assumption leads to an overestimation of the failure probability translated into practice by unnecessary repairs. To take into account the irreversible nature of the deterioration phenomenon, their representation using a positive process, the gamma type, is fitted to this purpose. The model developed in this paper authorizes a more rigorous estimation of probabilities of failure, reduces maintenance costs, and

permits a quantitative evaluation of the failure risk between two inspections and the optimal planning of the preventive maintenance programs to assure the low-risk level to be practical.

Nomenclature

- D = outer diameter of the pipeline
- GV = gamma model
- L = defect length
- M = Folias factor
- N_j = number of corroded defects within the kilometer J
- NV = normal model
- P_{fji} = probability of failure of a corrosion defect i of the kilometer J
- S_{\min} = specified minimum yielding stress
- t = wall thickness
- x = defect depth
- α = scale parameter
- β = form parameter
- μ_V = mean of corrosion growth rate
- $\mu_{X_{cr}}$ = mean of critical defect depths
- σ_V = standard deviation of corrosion growth rate

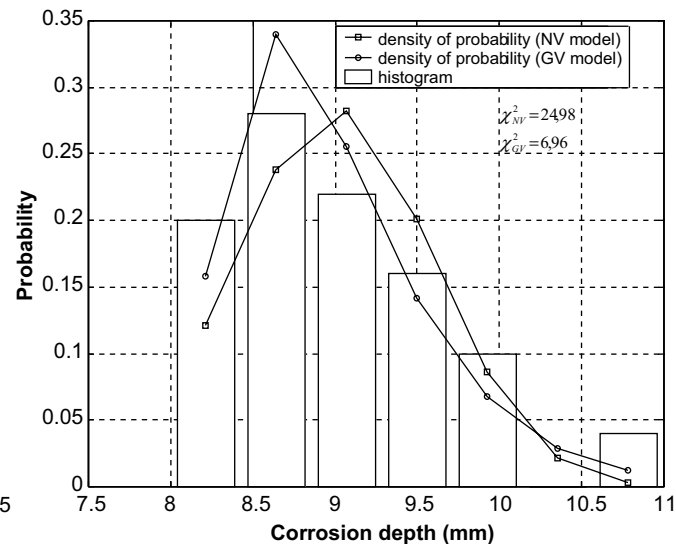
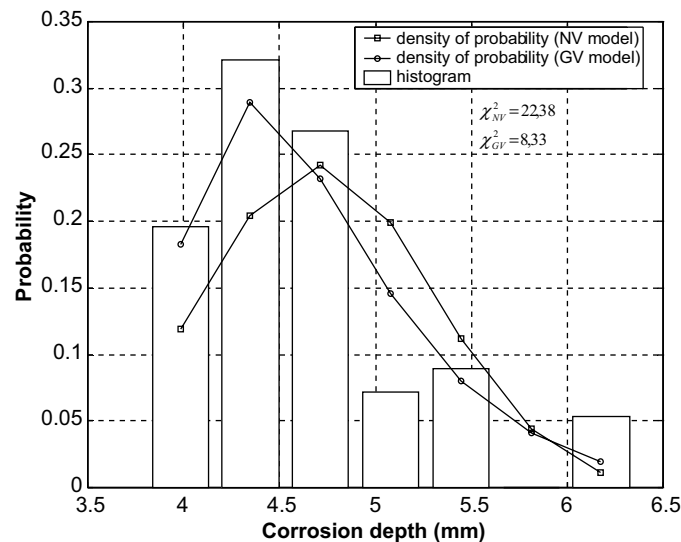


Fig. 9—Histogram and probabilistic distributions of corrosion depth after 5 years for two classes of initial depth (29 and 63%).

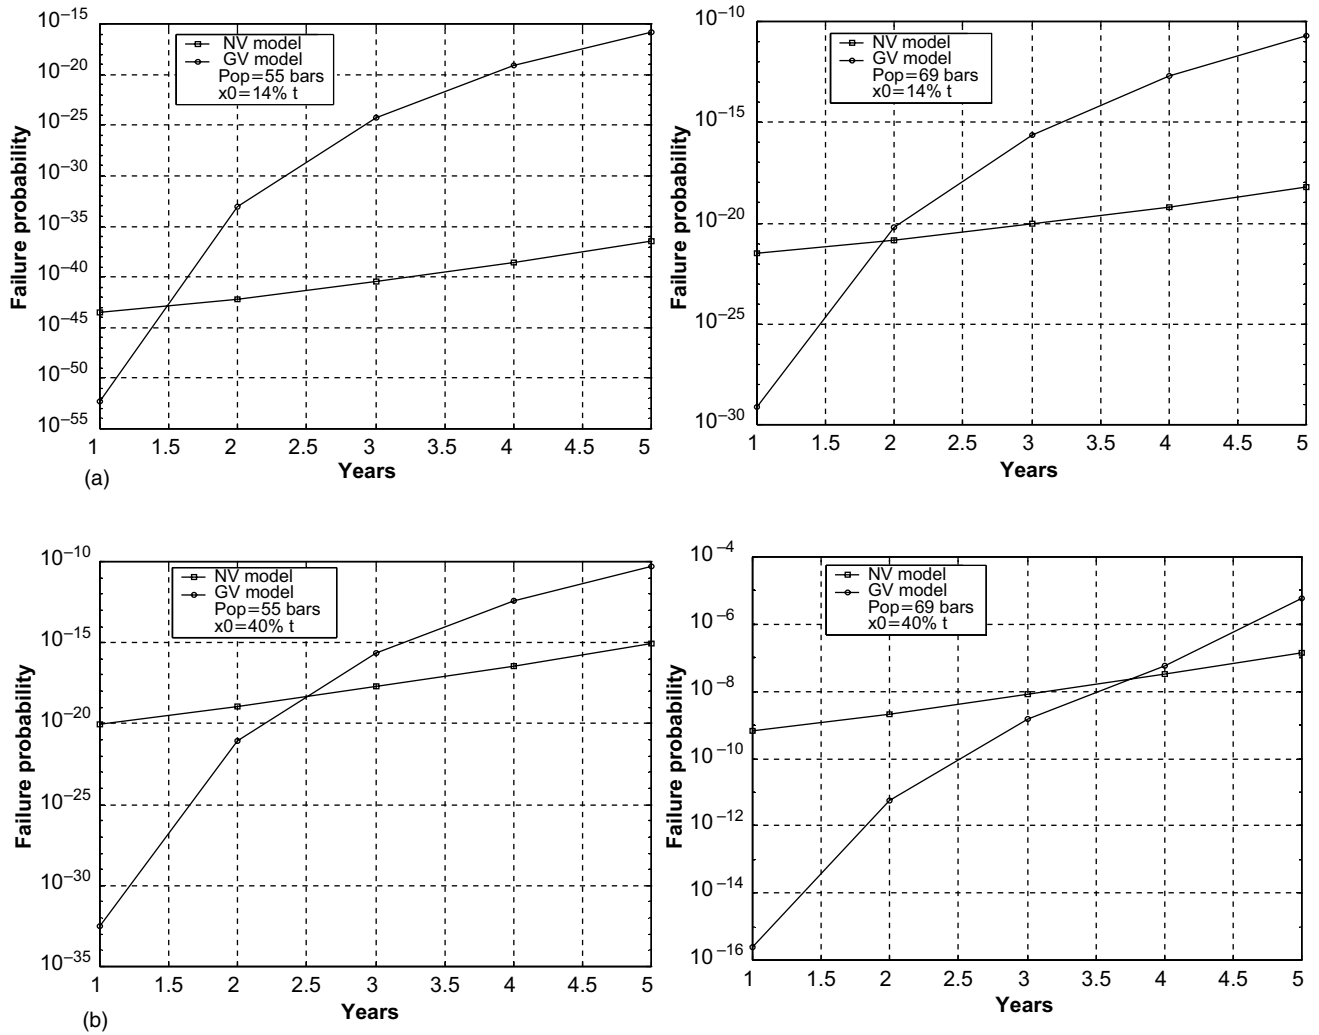


Fig. 10—Probability of failure with time for several initial corrosion depths and operating pressures. (a) Probability of failure with time for initial corrosion depths 14% t and operating pressures 55 and 69 bars; (b) probability of failure with time for initial corrosion depths 40% t and operating pressures 55 and 69 bars; (c) probability of failure with time for initial corrosion depths 53% t and operating pressures 55 and 69 bars; and (d) probability of failure with time for initial corrosion depths 79% t and operating pressures 55 and 69 bars.

σ_{X_c} = standard deviation of the critical defect depth
 Φ = is the cumulative function of the normal distribution

References

- Ahmed, M. and Melchers, R.E. 1996. Reliability estimation of pressurised pipelines subject to localised corrosion defects. *Int. J. Press. Vessels Pip.* **69** (3): 267–272. [http://dx.doi.org/http://dx.doi.org/10.1016/0308-0161\(96\)00009-9](http://dx.doi.org/http://dx.doi.org/10.1016/0308-0161(96)00009-9).
- Ahmed, M. and Melchers, R.E. 1997. Probabilistic analysis of underground pipelines subject to combined stresses and corrosion. *Eng. Struct.* **19** (12): 988–994. [http://dx.doi.org/http://dx.doi.org/10.1016/S0141-0296\(97\)00043-6](http://dx.doi.org/http://dx.doi.org/10.1016/S0141-0296(97)00043-6).
- Alamilla, J.L., Oliveros, J., and García-Vargas, J. 2009. Probabilistic modelling of a corroded pressurized pipeline at inspection time. *Struct. Infrastruct. Eng.* **5** (2): 91–104. <http://dx.doi.org/10.1080/15732470600924680>.
- ASME B31G-1991, *Manual for determining the remaining strength of corroded pipeline* (supplement to ANSI/ASME B31G code for pressure piping). 1991. New York: ASME.
- Desjardins, G. 2003. Reliability approach to optimized pipeline integrity planning based on probabilistic assessment of corrosion rates and future corrosion severity. Presented at the 6th International Conference on Pipeline Rehabilitation and Maintenance, Berlin, Germany, 6–10 October.
- DNV RP-F101, *Corroded Pipelines*. 2004. Høvik, Norway: Det Norske Veritas (DNV).
- Kadry, S., Chateaufneuf, A., and El-Tawil, K. 2007. Probabilistic Transformation Method in Reliability Analysis. *Turkish Journal of Engineering and Environmental Sciences* **31** (3): 135–148.
- Kiefner, J.F. and Vieth, P.H. 1990. Evaluating Pipe: New Method Corrects Criterion for Evaluating Corroded Pipe. *Oil Gas J.* **88** (32): 9–56.
- Kiefner, J.F., Duffy, A.R., Eiber, R.J. et al. 1973. Failure Stress Levels of Flaws in Pressurized Cylinders. In *STP 536: Progress in Flaw Growth and Fracture Toughness Testing*, ed. J. Kaufman, J. Swedlow, H. Corten et al., Paper ID STP49657S, 73–80. West Conshohocken, Pennsylvania: ASTM International.
- Lecchi, M. 2011. Evaluation of predictive assessment reliability on corroded transmission pipelines. *J. Nat. Gas Sci. Eng.* **3** (5): 633–641. <http://dx.doi.org/http://dx.doi.org/10.1016/j.jngse.2011.07.005>.
- Lee, O. and Pyun, J. 2002. Failure probability of corrosion pipeline with varying boundary condition. *KSME International Journal* **16** (7): 889–895. <http://dx.doi.org/10.1007/bf02949716>.
- Soong, T.T. 1973. *Random Differential Equations in Science and Engineering*, No. 103. New York: Mathematics in Science and Engineering, Academic Press.

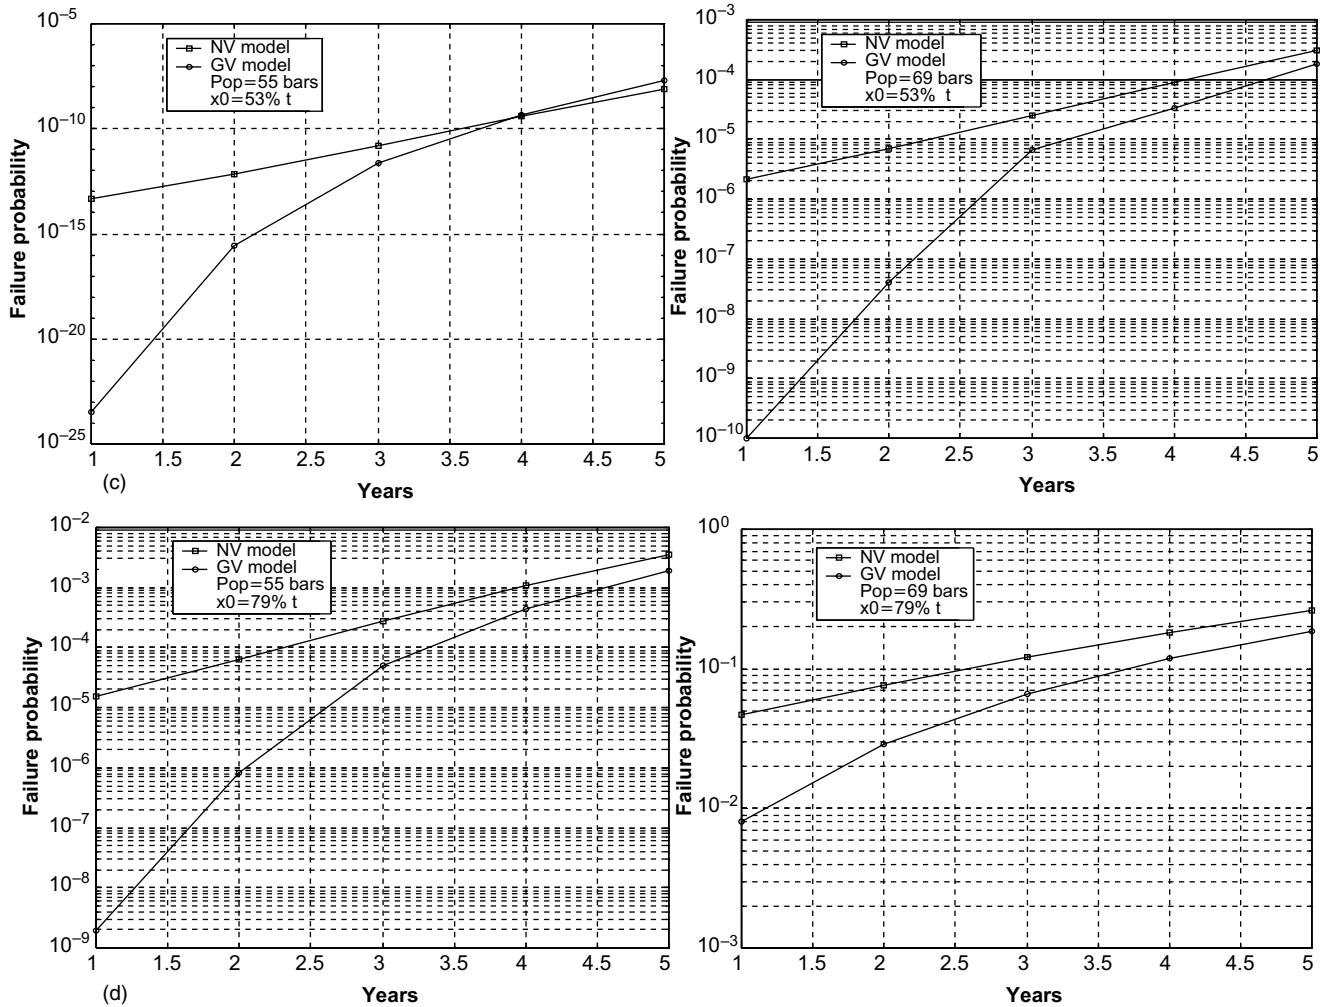


Fig. 10—Probability of failure with time for several initial corrosion depths and operating pressures. (a) Probability of failure with time for initial corrosion depths 14% t and operating pressures 55 and 69 bars; (b) probability of failure with time for initial corrosion depths 40% t and operating pressures 55 and 69 bars; (c) probability of failure with time for initial corrosion depths 53% t and operating pressures 55 and 69 bars; and (d) probability of failure with time for initial corrosion depths 79% t and operating pressures 55 and 69 bars.

van Noortwijk, J.M., van der Weide, J.A.M., Kallen, M.J. et al. 2007. Gamma processes and peaks-over-threshold distributions for time-dependent reliability. *Reliab. Eng. Syst. Saf.* **92** (12): 1651-1658. <http://dx.doi.org/http://dx.doi.org/10.1016/j.ress.2006.11.003>.

Worthingham, R.G., Fenyvesi, L.L., Morrison, T.B. et al. 2002. Analysis of corrosion rates on a gas transmission pipeline. *Pipeline and Gas Technology* (November/December): 45.

Younsi, K. and Smati, A. 2005. Modèle bayésien d'estimation du risque de défaillance sur un pipeline corrodé. Presented at the 5th Multidisciplinary International Conference, Bordeaux, France, 17 March. Presentation No. P81.

Appendix A—Model Based on the ASME B31 G Code

Failure stress S_f can be represented by ASME B31 G (1991) as follows:

$$S_f = 1,1S_{\min} \left[\frac{\left(1 - \frac{2x}{3t}\right)}{1 - M^{-1} \left(\frac{2x}{3t}\right)} \right], \dots \dots \dots (A-1)$$

where

$$M = \sqrt{1 + 0,8 \left(\frac{L}{\sqrt{Dt}} \right)^2} \dots \dots \dots (A-2)$$

The critical corrosion depth can then be expressed by

$$x_{cr} = \begin{cases} \frac{3}{2} \left(\frac{1,1S_{\min} - S_f}{1,1S_{\min} - M^{-1}S_f} \right) t & \text{if } \sqrt{0,8 \left(\frac{L}{\sqrt{Dt}} \right)^2} \leq 4 \\ \left(1 - \frac{S_f}{1,1S_{\min}} \right) t & \text{if } \sqrt{0,8 \left(\frac{L}{\sqrt{Dt}} \right)^2} > 4 \end{cases}, \dots \dots (A-3)$$

where S_{\min} =specified minimum yielding stress, M =Folias factor, x =defect depth, L =defect length, D =outer diameter of the pipeline, and t =wall thickness.

TABLE 3—NUMBER OF REPAIRS PER YEAR USING DIFFERENT APPROACHES					
Methodology	Number of Repairs				
	1st year	2nd year	3rd year	4th year	Total
B 31 G code	116	–	–	–	–
NV model	194	35	242	222	693
GV model	36	90	74	262	462

Appendix B—Load-Curve Model Based on Gamma Distribution of Corrosion Growth Rate and PTM

In a general case using the PTM, the density of probability $f_x(x)$ of a random variable X , related to another random and continuing

variable V with a known density of probability $f(v)$, can be obtained applying the following relation:

$$f_x(x) = f_v(g^{-1}(x)) \left| \frac{d}{dx} g^{-1}(x) \right| \dots\dots\dots(B-1)$$

Assuming a linear representation of the corrosion process given by Eq. 7, we obtain

$$v = g^{-1}(x) = \frac{x - x_0}{\tau} \dots\dots\dots(B-2)$$

and

$$\frac{dv}{dx} = \frac{dg^{-1}(x)}{dx} = \frac{1}{\tau} \dots\dots\dots(B-3)$$

From these relations, we can express the load-curve evolution with time, assuming gamma distribution of corrosion growth rate as follows:

$$f_{x(t)}(x) = \frac{1}{\tau} \frac{\beta^\alpha}{\Gamma(\alpha)} \left(\frac{x - x_0}{\tau} \right)^{\alpha-1} \exp\left(-\beta \left(\frac{x - x_0}{\tau} \right)\right) \dots\dots\dots(B-4)$$

or

$$f_{x(t)}(x) = \frac{1}{\tau} \text{Ga} \left(\frac{x - x_0}{\tau} \mid \alpha, \beta \right) \dots\dots\dots(B-5)$$

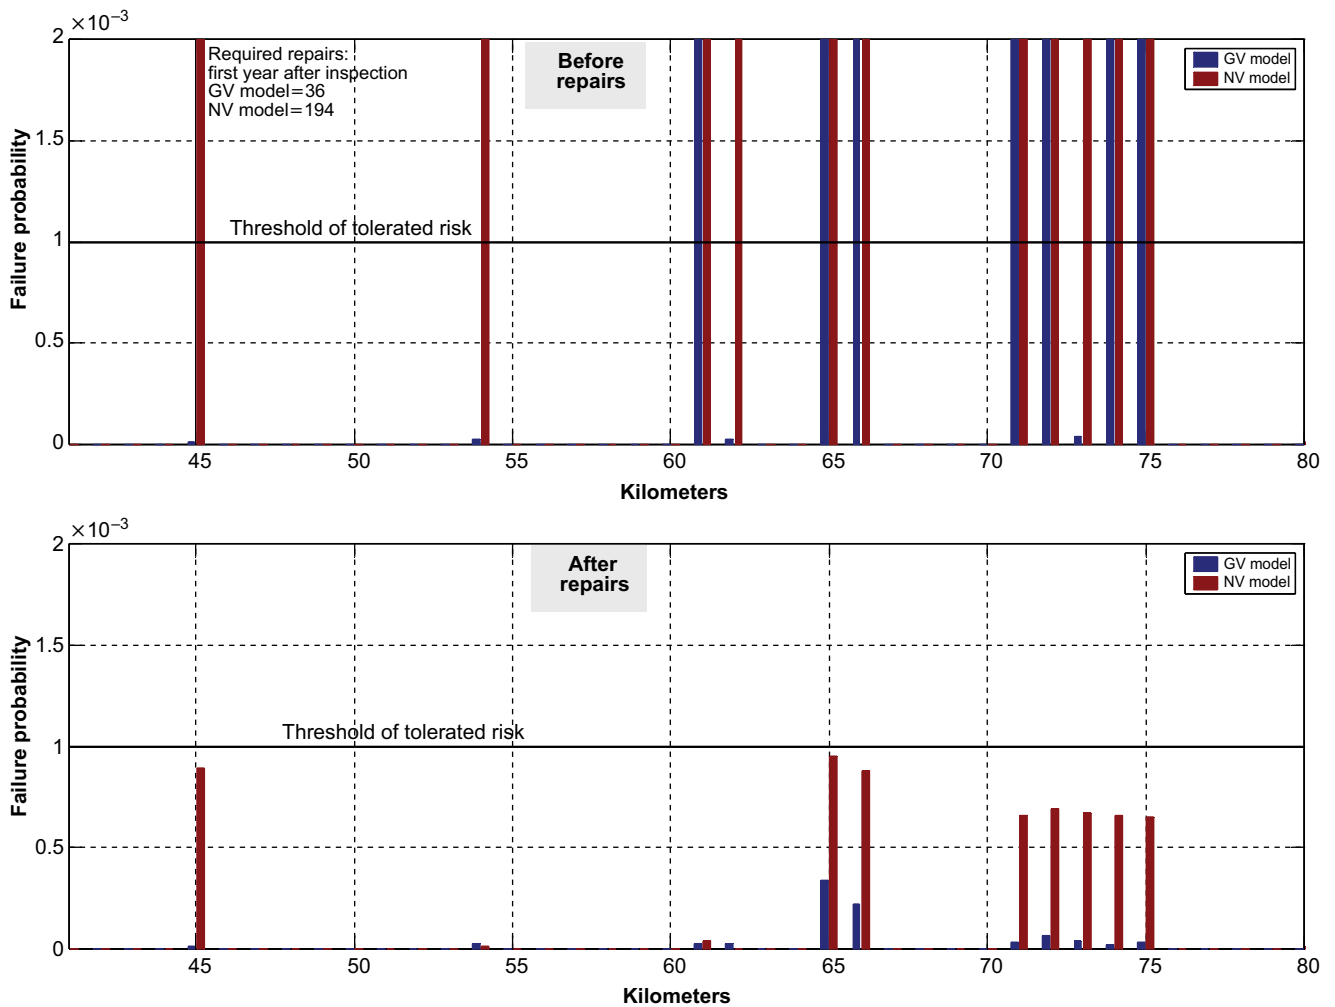


Fig. 11—Failure probability per km before and after repairs (1 year after inspection).

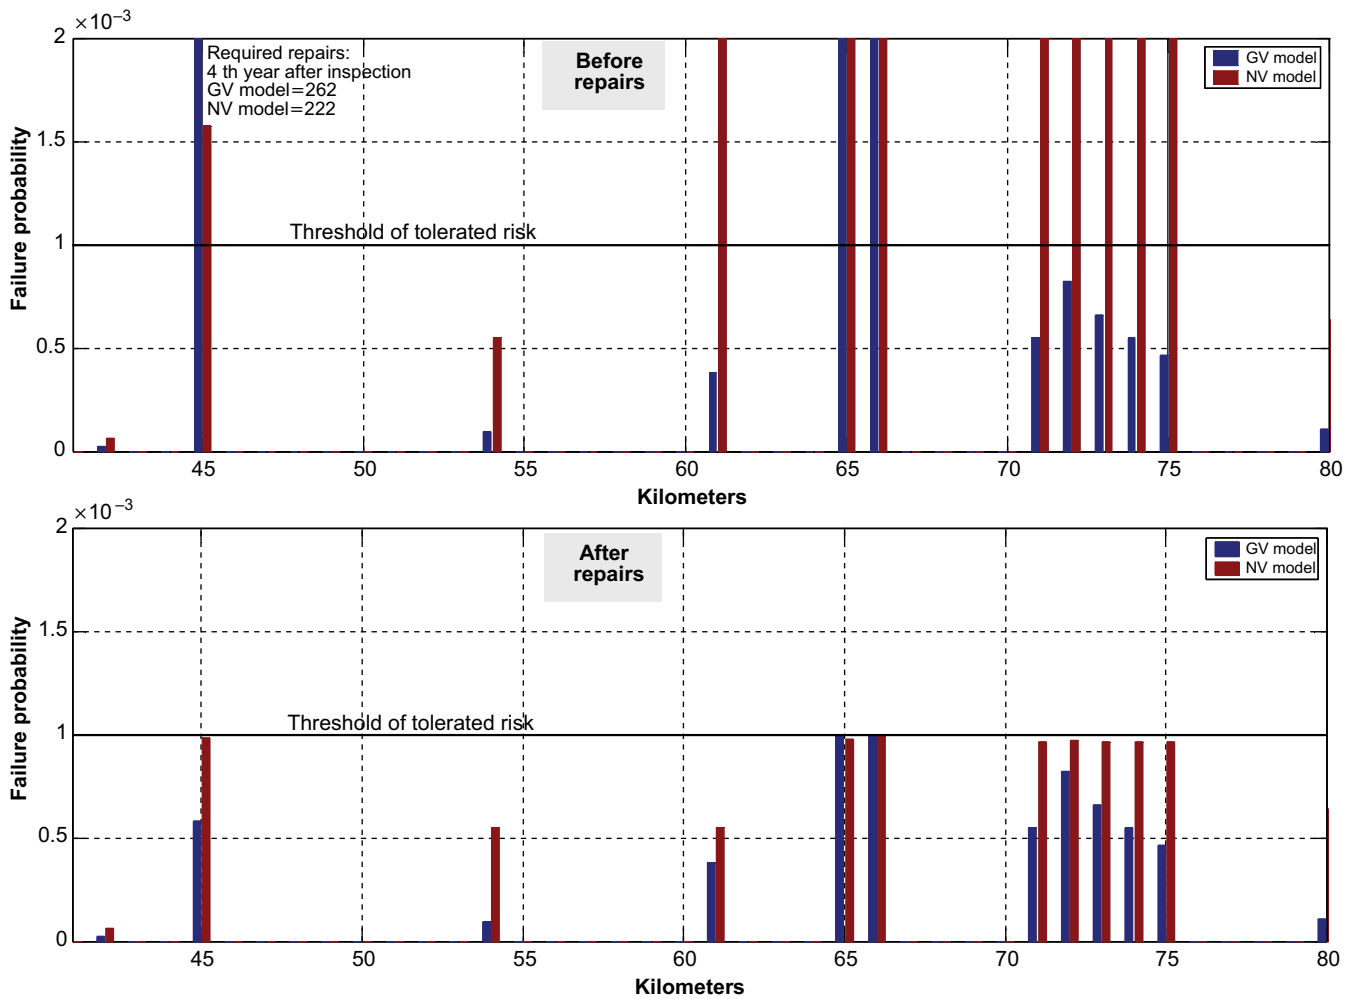


Fig. 12—Failure probability per km before and after repairs (4 years after inspection).

Karim Younsi has worked as a lecturer and researcher at the University of Boumerdes, Algeria, since 2004. He holds a BS degree in engineering and a Masters degree in reliability from the same institution.

Ammar Cheboub is a lecturer with the faculty of Chemistry and Hydrocarbons, University of Boumerdes, Algeria. He is also a member of the Research Laboratory on the Reliability of Petroleum Equipment and Materials. He holds a PhD degree in mechanical engineering from the University of Boumerdes.

Nordine Zemmour is a senior lecturer with the chemistry and hydrocarbons faculty at the University of Boumerdes, where he is a member of the OilEquipment Reliability and Materials Research Laboratory. He holds a PhD degree in process and apparatus from the Petroleum and Gas University of Moscow.

Abdelnacer Smati is a technical manager of the engineering company Pegaz Engineering. Before joining Pegaz, he taught in the Department of Transport and Equipment at the University of Boumerdes for 22 years. He holds a PhD degree in mechanical engineering.